

Available online at [www.sciencedirect.com](http://www.sciencedirect.com)

ScienceDirect

journal homepage: [www.elsevier.com/locate/hydro](http://www.elsevier.com/locate/hydro)

# Micro-porous layer (MPL)-based anode for microbial fuel cells

Jiseon You <sup>a</sup>, Carlo Santoro <sup>b,c</sup>, John Greenman <sup>a,d</sup>, Chris Melhuish <sup>a</sup>,  
Pierangela Cristiani <sup>e</sup>, Baikun Li <sup>b,c</sup>, Ioannis Ieropoulos <sup>a,b,\*</sup>

<sup>a</sup> Bristol BioEnergy Centre, Bristol Robotics Laboratory, University of the West of England, Bristol BS16 1QY, UK

<sup>b</sup> Department of Civil and Environmental Engineering, University of Connecticut, Storrs, CT 06269, USA

<sup>c</sup> Center for Clean Energy Engineering, University of Connecticut, Storrs, CT 06269, USA

<sup>d</sup> School of Life Sciences, University of the West of England, Bristol BS16 1QY, UK

<sup>e</sup> RSE-Ricerca sul Sistema Energetico S.p.A., Environment and Sustainable Development Department, Via Rubattino 54, 20134 Milan, Italy

## ARTICLE INFO

### Article history:

Received 14 March 2014

Received in revised form

23 July 2014

Accepted 24 July 2014

Available online 2 September 2014

### Keywords:

Microbial fuel cells (MFCs)

Anode modification

Micro-porous layer (MPL)

Energy from waste

Urine

## ABSTRACT

Two different anode materials, carbon veil (CV) and carbon cloth (CC), were modified with a micro-porous layer (MPL) in microbial fuel cells (MFCs). When the biofilm on the anodes matured, the maximum power output from the MPL modified carbon veil (CV20-MPL) and carbon cloth (CC-MPL) was 304.3  $\mu$ W (60.7 mW/m<sup>2</sup>) and 253.9  $\mu$ W (50.6 mW/m<sup>2</sup>), respectively. These were 2.2 and 1.8 times higher than the power output produced from the unmodified CV and CC, respectively. The 7-month operational tests indicated that the long-term stability of the MFCs was enhanced with the modified MPL anodes, which increased the anode surface roughness and provided higher surface area. Higher bacterial population was observed in the MFCs with the MPL anodes, which confirms the power generation results. This is the first time that the MPL has been used as an efficient anode material in MFCs.

Copyright © 2014, Hydrogen Energy Publications, LLC. Published by Elsevier Ltd. All rights reserved.

## Introduction

Despite the universal efforts for minimising the global energy problem, all of the currently available renewable energy sources (wind, hydro, photovoltaic and biomass) have their limitations; it thus becomes clear that more technological innovations through research need to be achieved. In this

respect, energy from organic waste can be a very attractive option. The useable form of energy from waste can include electricity, gas as well as heat and the most common method of implementation, is incineration of waste. For the last few decades, the system efficiency and unwanted gas emissions have been considerably improved, however this only has value when the waste is sufficiently dry; energy extraction is inefficient if the water content of waste is above 30% [1]. Thus

\* Corresponding author. Bristol BioEnergy Centre, Bristol Robotics Laboratory, T-Building, Frenchay Campus, Bristol BS16 1QY, UK. Tel.: +44 117 32 86318, +44 117 32 86322; fax: +44 117 32 83960.

E-mail address: [ioannis.ieropoulos@brl.ac.uk](mailto:ioannis.ieropoulos@brl.ac.uk) (I. Ieropoulos).  
<http://dx.doi.org/10.1016/j.ijhydene.2014.07.136>

0360-3199/Copyright © 2014, Hydrogen Energy Publications, LLC. Published by Elsevier Ltd. All rights reserved.

different approaches are required for recovering energy from 'wet waste' such as wastewater.

In this respect, microbial fuel cells (MFCs) that generate electricity by the break-down of organic matter (e.g. wastewater) have a great potential for future energy and environmental challenges. MFCs have numerous merits; firstly electricity is generated directly from organic matter, which results in a high efficiency of energy conversion. Secondly, MFCs can operate at ambient temperature conditions or even below 20 °C, and at low substrate concentration levels [2–4]. In terms of substrate variety, more recently, urine has been shown to be directly utilised for electricity generation, with promising results [5,6]. The organic carbon in urine is low, compared to other organic substrates [6], yet it seems to be performing better in terms of power output [7], which can be the topic of further study. Although the MFC technology has achieved remarkable improvements in terms of power output over the last two decades, practical implementation of the MFC technology, at large scale, has yet to be achieved due to the low levels of power generation and relatively high cost of materials.

Anode materials play an important role in the performance of MFCs by affecting the performance and cost of MFCs significantly. Carbon based materials such as carbon cloth [8], carbon fibre [9,10], graphite felt [11,12], and carbon paper [13] are the most commonly used materials in MFCs, due to their inertness toward bacteria and relatively low cost. Besides using these, diverse modifications have been made in order to enhance the anode performance. This includes ammonia treatment of anode surface [14,15], acid treatment [16,17], and adding nano-structured materials [18–20]. In general, a suitable MFC anode material requires large surface area for bacterial attachment and high electrical conductivity for the charge transfer, as well as good current collection capability. Since the anodes become biotic, they should be non-toxic to microorganisms, as well as inert to biochemical reactions, in order to prevent or minimise fouling; thus the structure of anodes needs to be carefully chosen. Also they should be robust for long term operation and economical, in terms of cost of production.

Micro-porous layer (MPL) has been widely used as a cathode material for hydrogen fuel cells [21–23] and more recently, microbial fuel cells [8,24]. In a cathode half-cell, MPL is usually placed between the gas diffusion layer (GDL) and the catalyst layer (CL). The function of MPL in this configuration is to provide sufficient porosity and hydrophobicity to allow better oxygen and water transport, as well as to reduce the electrical contact-resistance between the GDL and the adjacent CL. Hydrophobicity is not normally considered appropriate for anodes of MFCs but high porosity with good electrical conductivity are in fact desired properties in anodic materials. Therefore a hypothesis was formulated that the MPL could also work for MFC anodes.

In this study, carbon fibre veil (CV) and carbon cloth (CC) electrodes were modified with carbon powder, in order to introduce a micro-porous layer (MPL) of improved surface area and conductivity. The main objectives of the study were to test electrode modification with MPL, in order to evaluate its performance as an anode and investigate the feasibility of using MPL modified anodes in terms of power production,

surface morphology, biocompatibility, electrical conductivity, long-term stability and production costs.

## Materials and methods

### Anode preparation

Three different carbon fibre veil (CV) electrodes and two carbon cloth (CC) electrodes were tested in triplicates in this study. Plain carbon fibre veil electrodes (PRF Composite Materials Poole, Dorset, UK) with different amounts of carbon loading (20 g/m<sup>2</sup> and 30 g/m<sup>2</sup>) and untreated (non-wet proofed) carbon cloth (FuelCellEarth, Massachusetts, USA) were compared, under identical conditions. The MPL was a mixture of carbon black (Vulcan XC-72, main component) and PTFE (60% emulsion, Sigma–Aldrich, binder) and the preparation of this MPL material has been previously described [25]. The additional carbon loading from the MPL modification was approximately 18 g/m<sup>2</sup>. The five types of anode electrodes (three unmodified and two modified) were made of 12 layers of 4.18 cm<sup>2</sup> (width: 2.2 cm, length: 1.9 cm) of electrode material, resulting in a total macro surface area of 50.16 cm<sup>2</sup>. Details of each electrode are presented in Table 1.

### MFC design and operation

The MFCs consisted of 6.25 mL anode chambers and open-to-air cathodes. The anode compartments had inlets and outlets ( $d = 4$  mm) at the bottom and top, respectively for continuous feeding (Fig. 1(a)). A cation exchange membrane (CMI-7000, Membrane International), 25 mm diameter, was sandwiched between the anode and cathode frames. The cathode electrodes, which were identical for all 15 MFCs, were made of hot-pressed activated carbon onto untreated carbon cloth and had a total macro surface area of 4.9 cm<sup>2</sup>. Titanium (0.45 mm thickness) wire was used for connection of the electrodes and current collection (Fig. 1(b)).

Activated sewage sludge supplied from the Wessex Water Scientific Laboratory (Saltford, UK) was used as the inoculum. Sludge was mixed with 0.1 M acetate prior to use, resulting in an initial pH level of 7.2; the same mixture was used as the initial feedstock. Following the inoculation of the MFCs and the maturing of the biofilm communities on the anodes for a week, untreated human urine was used as the sole energy source. Urine was donated from male and female healthy individuals, on a normal diet and without any medical conditions, and was pooled together prior to use. Continuous flow of the anolyte was maintained using a 16-channel peristaltic pump (205 U, Watson Marlow, Falmouth, UK) with a flow rate of 11.5 mL/h. For maximising power output in the long term, different external resistance values, which matched the internal resistance values of MFCs for the different anode materials, were connected throughout the work. Power output of the MFCs was monitored in real time in volts (V) against time using an ADC-24 Channel Data Logger (Pico Technology Ltd., Cambridgeshire, UK). Each experimental condition was tested in triplicate and all experiments were carried out in a temperature controlled laboratory, with  $22 \pm 2$  °C.

**Table 1 – Details of experimental conditions employed in the study.**

Abbreviation	Composition	Original carbon content (g/m <sup>2</sup> )	Total carbon content (g/m <sup>2</sup> )
CV20	Unmodified carbon veil	20	20
CV30	Unmodified carbon veil	30	30
CV20-MPL	Modified carbon veil with MPL	20	38
CC	Unmodified carbon cloth	115	115
CC-MPL	Modified carbon cloth with MPL	115	133

## Analysis

### Scanning electron microscopy (SEM)

Scanning electron microscopy (model name-XL30, Philips) was used to examine the shapes and structures of the unmodified/modified anode material surfaces. Samples of 0.5 cm<sup>2</sup> area of each material were cut and fixed on aluminium mounts using contact adhesive. Samples were prepared for microscopy by sputter coating in gold using an Emscope SC500 sputter coating unit.

### Direct cell counting

For the hemocytometric cell number measurements, 0.1 mm deep Neubauer-improved hemocytometers were used (Marienfeld-superior, Germany). The two independent consecutive measurements were performed using the two different sides of each hemocytometer. The raw effluent was diluted 10–20 times with phosphate buffered saline. The bacterial cell population was determined by counting individual cells using a grid-field.

### Four-wire resistance measurement

In order to measure electrical conductivity of the tested anode materials, 4-wire resistance measurement was carried out with a digital multimeter (M-3850D, METEX, Korea) and bench power supply (PSM-3004, GW INSTEK, Taiwan). A small piece of each material (15 mm × 15 mm) was placed between two clamps. Voltage drop between the two points was measured when constant current was supplied to the material from the power supply. This method is considered more accurate than the 2-wire method for low resistance measurements since it reduces the effect of test lead resistance.

### Principal component analysis (PCA)

PCA was used in order to process large sets of data and find distinctive patterns. PCA is a statistical tool that simplifies the visualisation of the variables accountable for relations among the different samples by generating uncorrelated components named as principal components. The two principal

components, orthogonal one to the other, represent the largest possible variance (PC-1) and the largest possible inertia (PC-2) respectively [26]. In the current study, power (density, absolute, specific, initial, middle and final), resistivity and material cost were used as variables in the PCA matrix. Auto-scaling PCA (PLS\_Toolbox 3.54 in Matlab, Eigenvector Research Inc., USA) was applied to this dataset.

### Polarisation measurement and power output calculations


Polarisation experiments were performed periodically by connecting a DR07 decade variable resistor box (ELC, France), between the anode and cathode electrodes. Polarisation data were generated by varying the external resistance from 30 k $\Omega$  to 10  $\Omega$  at time intervals of 5 min after the MFCs had established a steady-state open-circuit voltage.

The current ( $I$ ) in amperes (A) was determined using Ohm's law,  $I = V/R$ , where  $V$  is the measured voltage in volts (V) and  $R$  is the known value of the external resistor expressed in ohms ( $\Omega$ ). Power ( $P$ ) in watts (W) was calculated by multiplying voltage with current;  $P = I \times V$ . Power density ( $P_D$ ) was calculated according to the electrode total macro surface area;  $P_D = P/\alpha$ , where  $\alpha$  is the total electrode macro surface area in square metres (m<sup>2</sup>). Internal resistance was calculated using  $R_{INT} = (V_{O/C}/I_L) - R_L$ , (from Kirchhoff's voltage law) where  $V_{O/C}$  is the open-circuit of the MFC,  $I_L$  is the current under a load and  $R_L$  is the value of the load resistor. The value of  $R_{INT}$  was also validated from the  $V/I$  curves of the polarisation experiments.

## Results and discussion

### Performance of the MPL modified anodes

The MPL modification improved the MFC performance significantly when compared with the unmodified anode materials as shown in Fig. 2. From the beginning, the MPL

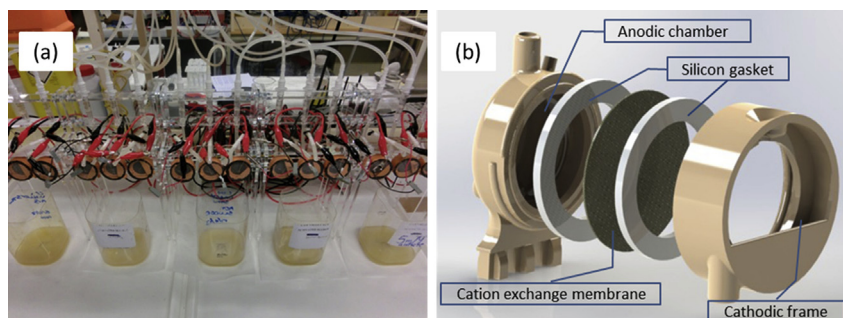

**Fig. 1 – (a) MFC experimental set-up; (b) 3D CAD assembly of the single chamber MFC.**

modified anodes showed higher power performance than the plain ones, which was consistent throughout the entire line of work. During the middle stage, when the biofilm on the anodes was considered to be mature, the MFCs performed their best. The best performing anode material, CV20-MPL, produced a maximum power of 304.3  $\mu\text{W}$  (60.7  $\text{mW}/\text{m}^2$  normalised to the anode total macro surface area, mean value  $290 \mu\text{W} \pm 13$ ), which was 1.2 fold higher than the second best performing anode material, CC-MPL with a maximum power of 253.9  $\mu\text{W}$  (50.6  $\text{mW}/\text{m}^2$ , mean value  $249 \mu\text{W} \pm 8$ ). The maximum power produced by the unmodified electrodes, CV20, CV30 and CC, was 140.0  $\mu\text{W}$  (27.9  $\text{mW}/\text{m}^2$ , mean value  $130 \mu\text{W} \pm 10$ ), 180.7  $\mu\text{W}$  (36.0  $\text{mW}/\text{m}^2$ , mean value  $171 \mu\text{W} \pm 10$ )

and 143.4  $\mu\text{W}$  (28.6  $\text{mW}/\text{m}^2$ , mean value  $137 \mu\text{W} \pm 6$ ), respectively. This demonstrates that the MPL modification can result in significant anode improvements.

The resulting 2.2 and 1.8 fold higher power was achieved by modifying the plain CV with 20  $\text{g}/\text{m}^2$  of carbon loading and CC carbon materials, which is also supported by the improved performance from the off-the-shelf higher-loading carbon (30  $\text{g}/\text{m}^2$ ), compared to the unmodified electrodes. It is therefore valid to assume that the higher carbon content from the MPL modification contributed – to a degree – to the higher power generation of MFCs. Although this was expected, it could not have been the only reason for the improved anode performance. The maximum power output of each anode material during the middle stage was compared (Table 2). For the specific power density, presented as the power output per 1 g of anode carbon, the same amount of carbon did not result in the same level of increase in the output, especially for the CC based materials, where specific power density was far lower than the CV based materials.

### Surface morphology

Another possible explanation for the performance enhancement with MPL modification may be its surface characteristics. The SEM images of the sterile CV and CC anodes (Fig. 3(a)–(c)) showed that the MPL covered the anode surface as well as the gaps between carbon fibres (Fig. 3(d) and (e)). With higher magnification, the MPL surface seems uneven and more porous, which could result in better and higher surface area for bacterial attachment (Fig. 3(f)).

The SEM images could explain why CC based materials did not perform as well as CV based materials, even though they had higher carbon content. Carbon fibres of the CC were densely woven (Fig. 3(c)), so that even though bacteria could penetrate deep into the strata, fuel supply from percolation would have been uneven at those inner layers, which is not the case for the less dense CV. Uneven and decreasing concentrations of fuel would have inevitably resulted in an eroding inner CC biofilm core.

### Biocompatibility

In order to address whether the increased anode surface through MPL modification was beneficial for the growth of anodophilic bacteria, the bacterial production rate from the effluent of all MFCs was measured over a 2-month operational period, which allowed MFCs to run in various conditions.

With the direct cell counting method, all the suspended cells in the anolyte, both living and dead, were non-selectively

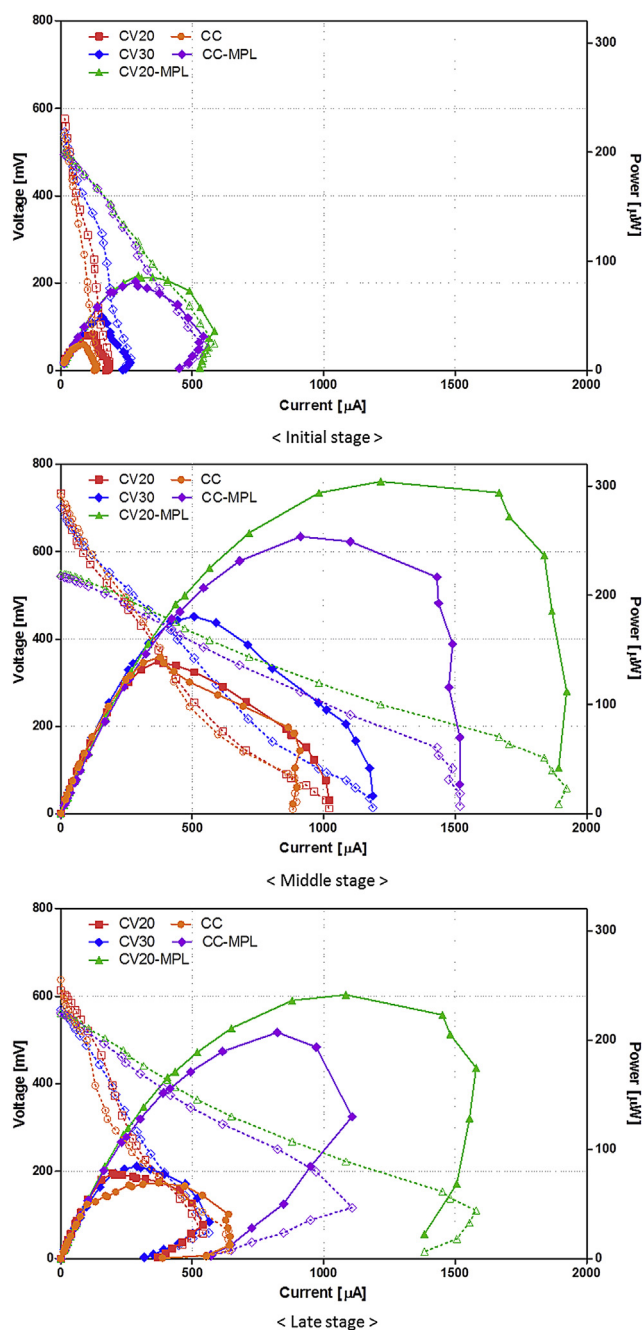


Fig. 2 – Power curves of different anode materials at different stages of the experiments.

Table 2 – Maximum power output of MFCs during the middle stage with different anode materials.

Electrode	Absolute power ( $\mu\text{W}$ )	Power density ( $\text{mW}/\text{m}^2$ )	Specific power density ( $\text{mW}/\text{g}$ )
CV20	140.0	27.9	1.40
CV30	180.7	36.0	1.20
CV20-MPL	304.3	60.7	1.60
CC	143.4	28.6	0.25
CC-MPL	253.9	50.6	0.38



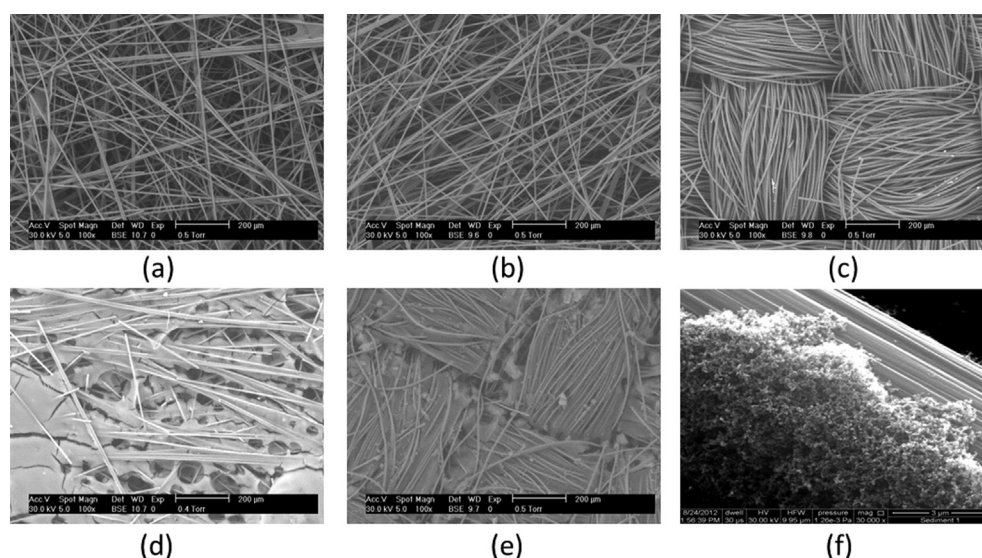


Fig. 3 – SEM images of anode electrodes; (a) CV20; (b) CV30; (c) CC; (d) CV20-MPL; (e) CC-MPL; (f) MPL structure on CC-MPL.

counted (including non electro-active species). Nevertheless, a relationship between bacterial cell production and power output could be drawn from the results shown in Fig. 4. Although the relation between the two was not directly proportional, higher bacterial populations tended to contribute to higher power output levels. Therefore a conclusion could be drawn that higher anodic surface area, through MPL modification, had positive influence on bacterial growth on the anodes, increasing the anodic load of attached cells from which daughter cells are derived or increasing the growth rate of the attached biofilm layers, thus producing higher numbers of shed daughter cells in the perfusate.

The relationship between bacterial cell production rate and power output might indicate that the portion of anodophiles constituting the whole microcosm population was larger in the MFCs with modified anodes due to the change brought about by the anode modification. In this case, it may be assumed that MPL modification is selective to anodophiles. In-depth bacterial analysis would need to be carried out to investigate this.

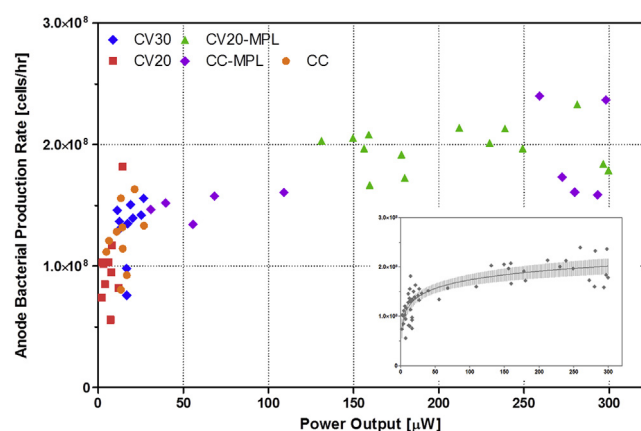


Fig. 4 – Bacterial production rate from the effluent of MFCs with different anode materials. Inset shows the regression analysis of the data with 95% CI.

Cathodic MPL modification is traditionally performed with PTFE (polytetrafluoroethylene), which is used for making the layer hydrophobic as well as binding carbon powder and current collection (e.g. CV or CC). This hydrophobic characteristic appeared in the modified anodes. When MPL modification was completed, the water-uptake element of the MPL modified anodes was low. However this did not seem to have a significant negative effect on bacterial growth, at least over the long-term. The mixed number of attachment points with different surface hydrophilic/hydrophobic properties (carbon or PTFE) may result in greater diversity of surfaces and therefore greater diversity of types of bacteria that can attach. Bacteria can actually colonise pure PTFE surfaces, which is problematic in protecting medical equipment from bacterial contamination [27,28], and the results derived from bacterial population counting are consistent with this, showing that the MPL modified anodes (with PTFE) were biocompatible.

### Electrical conductivity

Another possible downside predicted for using PTFE in anodic materials, was the decrease in the anodic electrical conductivity. According to the manufacturer of PTFE, volume resistivity of PTFE at 20 °C is more than  $10^{18} \Omega \text{ m}$  [29]. Thus PTFE could work as an insulator in the modified materials due to its high resistivity.

Electrical conductivity of anodes is an essential feature because it greatly affects ohmic losses in MFC systems; since conductivity is the reciprocal of resistivity, the former can be derived by measuring the latter. Electrical resistivity (volume resistivity) of each anode material was measured at room temperature ( $22 \pm 2^\circ \text{C}$ ) (Fig. 5).

Although all the tested anode materials consisted of the same carbon base, the resistivity varied due to the particle size, aggregate structure and porosity [30]. As a result, electrical resistivity slightly increased both in CV and CC through the MPL modification, which might be the result of the PTFE addition. In this particular case, and even though the

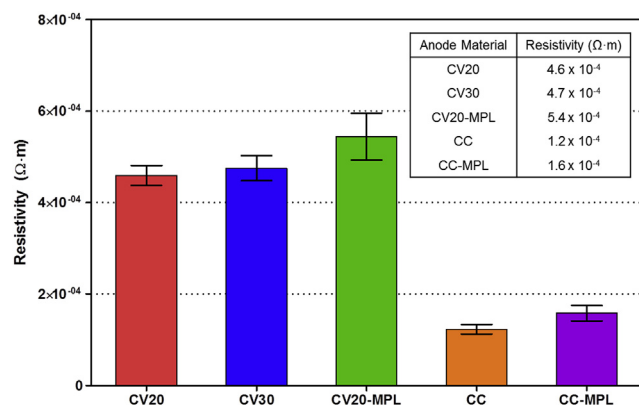


Fig. 5 – Electrical resistivity of each anode material.

differences in resistivity were small, it is clear that the PTFE loading was counteracting the increase in surface area, achieved from the MPL modification. It can also be noted that the resistivity of the off-the-shelf unmodified electrodes was much lower for the under-performing CC than the CV20 or CV30, and this may be attributed to the higher carbon loading. Since micro-structure and characteristics of MPL changes with different PTFE loadings [31,32], the amount of PTFE needs to be carefully selected for an optimum modification.

It should be noted that resistivity is an intrinsic property, unlike resistance. Resistance of the anodes used in the test could vary based on their shape and size. In this study, the same macro surface size was used for all materials but the volume of anodes was different, due to different thicknesses of the anode materials.

### Long-term operation

Durability is critical for long term MFC operation. The MPL modified anodes were operated for 7 months to investigate the long term stability. Good MFC anodes are expected to have a low level of fouling, however meeting this requirement is not trivial since a high void volume consisting of fine spaces for sustaining the microbial growth and multiplication, is

essential. In an ideal continuous-fed system with the optimum flow rate, this could be avoided or minimised since clogging is a result of slow flow and poor hydrodynamic control. Even though the MFC systems were under continuous flow conditions, anode chamber clogging – due to urine precipitation – was observed, which would have been accompanied by membrane ageing. During the 7-month operational period, MFCs were opened 3 times, in order to clear the precipitation that was accumulating on the membranes and anode chambers. There might have also been an element of an accumulating biofilm on the anode electrodes, but this is a parameter that will be more closely monitored in the next stages of this study. After cleaning the MFCs, performance of all units dropped but then quickly recovered to their previous performance levels.

Fig. 6 shows the power generating performance profile of tested anode materials at different stages of the experimental period. All MFCs showed a similar pattern: performance increased in the early stages and then decreased in the later stages. In the 2nd week, power output increased gradually as MFC anodes were matured. After 1 month (referred to as middle stage), the power output of all MFCs improved significantly, which implied that biofilms on the anodes were fully established. After nearly 7 months, power output declined. However, the extent of performance decline differed for each anode material. Over 50% of the decline in performance occurred in unmodified CV30, CV20 and CC ( $50.4 \pm 6\%$ ,  $54.1 \pm 3\%$ , and  $55.6 \pm 1\%$ , respectively), whereas only  $36.0 \pm 5\%$  (CV20-MPL) and  $41.2 \pm 4\%$  (CC-MPL) of performance reduced in the MPL modified anodes. Their power performance change is also verified in the polarisation curves (Fig. 2). Maximum power output decreased by only 20.7% and 18.5% for the CV20-MPL and CC-MPL respectively, whilst 53.2%, 43.9% and 51.5% reduction was recorded for CV30, CV20 and CC between the middle and late stages. Therefore, this result indicated that MPL modification improves anode durability for long-term operation.

Another factor to consider when to select anode materials for an MFC system is substrate. Urine which was used as a substrate in this work tends to precipitate naturally. If a defined substrate with less insoluble matter is used, a different size of anode cavities or surface morphology may be more desirable.

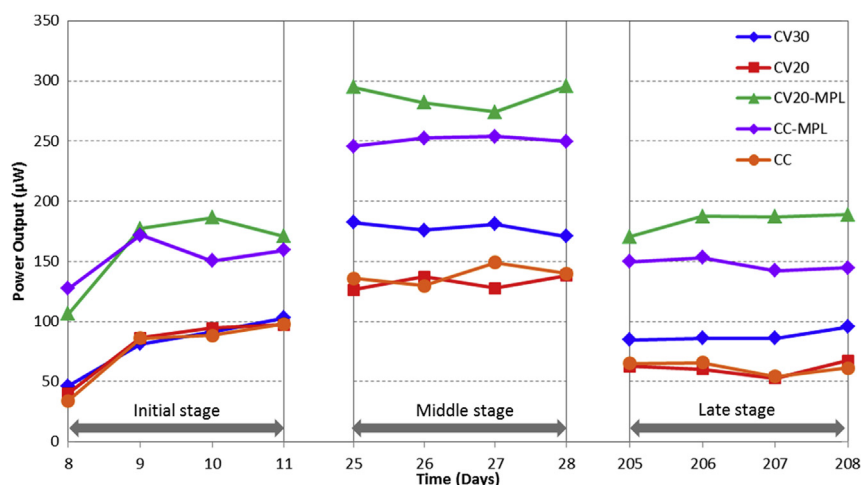


Fig. 6 – Power production from MFCs with different anode materials in different stages of the work; temporal profile.

**Table 3 – Anode material cost spent in this study and other factors to consider.**

Anode material	Anode material cost (USD/m <sup>2</sup> )	Power per cost (mW/USD)	Performance decline after 7 months of operation (%)
CV20	12.3	2.27	54.1 ± 3
CV30	16.2	2.22	50.4 ± 6
CV20-MPL	52.1	1.17	36.0 ± 5
CC	588.4	0.05	55.6 ± 1
CC-MPL	628.2	0.08	41.2 ± 4

### Economic evaluation


So far the MPL modified anodes were compared with the unmodified anodes in terms of power production, surface morphology, biocompatibility, electrical conductivity and long term durability. The economical aspect should not be overlooked even though the majority of MFC research is still at laboratory level. When the economical aspect is considered for a MFC system, various elements need to be taken into account. The costs of the anode materials tested were compared (Table 3), with respect to the material cost only, but not the cost of fabrication of the MPL modification. The modification of 1 m<sup>2</sup> of anode materials, required approximately 40USD. This additional cost gave 220% and 180% of performance improvement than unmodified CV and CC anodes, respectively and also enhanced the stability of the MFC systems. This cost could be reduced significantly for mass production. Although it is too early to justify that MPL modification is affordable or competitive in terms of cost, this consideration is important.

Despite the fact that many researchers studying fuel cells, including hydrogen based fuel cells, claim environment-friendly advantages of the technology, sustainability in manufacturing, operating, and discarding of fuel cell systems is often forgotten. Especially for the MFC technology, which is believed to have green energy merits for the future, this is very important. Although a direct comparison of MPL modified anodes to other anode materials is difficult in terms of

environmental impact, it is reasonable to assume that the extent of pollution did not increase much by the modification since no toxic chemical or heavy metal was used.

### Principle component analysis (PCA) and general analysis

All the data obtained were used as input in the PCA analysis. Power (density, absolute, specific, initial, middle, final and per unit cost), resistivity, carbon loading, anode production rate and material cost for all the samples (CV20, CV30, CV20-MPL, CC and CC-MPL) were used as variables in the PCA matrix (Fig. 7). Three different zones in the PCA can be identified: i) CV20-MPL showed the best performance levels (initial, middle, final, specific and density) and highest anode production rate; ii) CC and CC-MPL showed the highest material cost, highest conductivity (inversely proportional to the resistivity) and carbon loading; iii) CV20 and CV30 showed the best power per unit cost but also higher decline in long-term operation. CV generally had a lower cost so it seems to be an appropriate candidate as anode material. CC (with and without MPL) were not suitable as anodes in the MFCs mainly due to their high cost and also poor durability despite their best conductivity properties. The MPL addition on the CV increases the cost of production slightly, however showed the highest power output and material durability. Therefore it was concluded that CV20-MPL was the best anode material among the five different materials tested in this study.

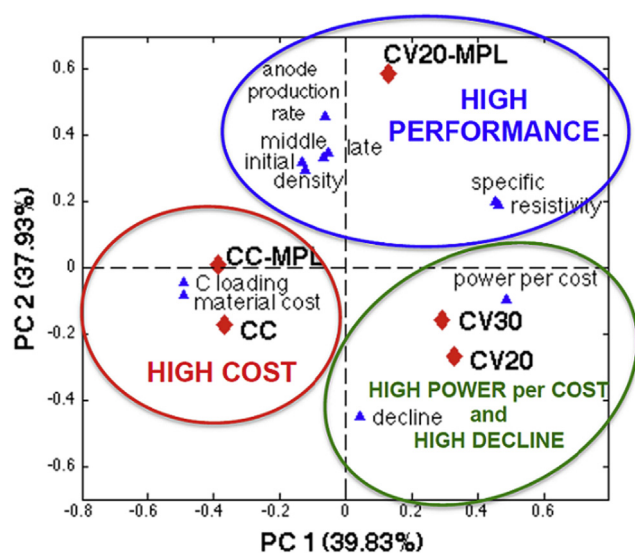

**Fig. 7 – Principal components analysis biplot for the different anodes investigated.**

### Conclusions

Carbon based materials (CV and CC) were modified with MPL and their performance was evaluated as MFC anodes. The results showed that MPL modification of anodes increased power performance, bacterial production rate of anode and MFC stability. Since PTFE caused higher resistivity and hydrophobicity, optimisation of its use in terms of concentration or heating temperature during the MPL making process, or finding an alternative binder that could replace PTFE, need to be further investigated. The feasibility study indicated that MPL modification for anode materials is desirable. This was the first study that the MPL was used as an anode electrode in MFCs.

### Acknowledgements

The authors would like to thank the Engineering and Physical Sciences Research Council (EPSRC) UK, for the financial



support of this work through the project with grant numbers EP/I004653/1 and EP/L002132/1. Parts of the urine study are funded by the Bill & Melinda Gates Foundation grant no. OPP1094890.

## REFERENCES

- [1] McCarty PL, Bae J, Kim J. Domestic wastewater treatment as a net energy producer – can this be achieved? *Environ Sci Technol Sep.* 2011;45(17):7100–6.
- [2] Larrosa-Guerrero A, Scott K, Head IM, Mateo F, Ginesta A, Godinez C. Effect of temperature on the performance of microbial fuel cells. *Fuel Dec.* 2010;89(12):3985–94.
- [3] Zhang L, Shen J, Wang L, Ding L, Xu K, Ren H. Stable operation of microbial fuel cells at low temperatures (5–10 °C) with light exposure and its anodic microbial analysis. *Bioproc Biosyst Eng Sep.* 2013;37(5):819–27.
- [4] Pant D, Van Bogaert G, Diels L, Vanbroekhoven K. A review of the substrates used in microbial fuel cells (MFCs) for sustainable energy production. *Bioresour Technol Mar.* 2010;101(6):1533–43.
- [5] Kuntke P, Smiech KM, Bruning H, Zeeman G, Saakes M, Sleutels THJA, et al. Ammonium recovery and energy production from urine by a microbial fuel cell. *Water Res May* 2012;46(8):2627–36.
- [6] Ieropoulos I, Greenman J, Melhuish C. Urine utilisation by microbial fuel cells; energy fuel for the future. *Phys Chem Chem Phys Jan.* 2012;14(1):94–8.
- [7] Ieropoulos I, Gajda I, You J, Greenman J. Urine—waste or resource? The economic and social aspects. *Rev Adv Sci Eng Sep.* 2013;2(3):192–9.
- [8] Santoro C, Agrios A, Pasaogullari U, Li B. Effects of gas diffusion layer (GDL) and micro porous layer (MPL) on cathode performance in microbial fuel cells (MFCs). *Int J Hydrogen Energy Oct.* 2011;36(20):13096–104.
- [9] Ieropoulos I, Greenman J, Melhuish C. Improved energy output levels from small-scale microbial fuel cells. *Bioelectrochemistry May* 2010;78(1):44–50.
- [10] Winfield J, Ieropoulos I, Greenman J, Dennis J. The overshoot phenomenon as a function of internal resistance in microbial fuel cells. *Bioelectrochemistry May* 2011;81(1):22–7.
- [11] Biffinger JC, Ray R, Little B, Ringeisen BR. Diversifying biological fuel cell designs by use of nanoporous filters. *Environ Sci Technol Feb.* 2007;41(4):1444–9.
- [12] Aelterman P, Versichele M, Marzorati M, Boon N, Verstraete W. Loading rate and external resistance control the electricity generation of microbial fuel cells with different three-dimensional anodes. *Bioresour Technol Dec.* 2008;99(18):8895–902.
- [13] Santoro C, Guilizzoni M, Correa Baena JP, Pasaogullari U, Casalegno A, Li B, et al. The effects of carbon electrode surface properties on bacteria attachment and start up time of microbial fuel cells. *Carbon N Y Feb.* 2014;67:128–39.
- [14] Cheng S, Logan BE. Ammonia treatment of carbon cloth anodes to enhance power generation of microbial fuel cells. *Electrochem Commun Mar.* 2007;9(3):492–6.
- [15] Velasquez-Orta SB, Curtis TP, Logan BE. Energy from algae using microbial fuel cells. *Biotechnol Bioeng Aug.* 2009;103(6):1068–76.
- [16] Scott K, Rumbu GA, Katuri KP, Prasad KK, Head IM. Application of modified carbon anodes in microbial fuel cells. *Process Saf Environ Prot Jan.* 2007;85(5):481–8.
- [17] Feng Y, Yang Q, Wang X, Logan BE. Treatment of carbon fiber brush anodes for improving power generation in air–cathode microbial fuel cells. *J Power Sources Apr.* 2010;195(7):1841–4.
- [18] Sun J-J, Zhao H-Z, Yang Q-Z, Song J, Xue A. A novel layer-by-layer self-assembled carbon nanotube-based anode: preparation, characterization, and application in microbial fuel cell. *Electrochim Acta Mar.* 2010;55(9):3041–7.
- [19] Fan Y, Xu S, Schaller R, Jiao J, Chaplen F, Liu H. Nanoparticle decorated anodes for enhanced current generation in microbial electrochemical cells. *Biosens Bioelectron Jan.* 2011;26(5):1908–12.
- [20] Xiao L, Damien J, Luo J, Jang HD, Huang J, He Z. Crumpled graphene particles for microbial fuel cell electrodes. *J Power Sources Jun.* 2012;208:187–92.
- [21] Weber AZ, Newman J. Effects of microporous layers in polymer electrolyte fuel cells. *J Electrochem Soc Apr.* 2005;152(4):A677.
- [22] Wang XL, Zhang HM, Zhang JL, Xu HF, Tian ZQ, Chen J, et al. Micro-porous layer with composite carbon black for PEM fuel cells. *Electrochim Acta Jun.* 2006;51(23):4909–15.
- [23] Cho KT, Mench MM. Investigation of the role of the micro-porous layer in polymer electrolyte fuel cells with hydrogen deuterium contrast neutron radiography. *Phys Chem Chem Phys Mar.* 2012;14(12):4296–302.
- [24] Papaharalabos G, Greenman J, Melhuish C, Santoro C, Cristiani P, Li B, et al. Increased power output from micro porous layer (MPL) cathode microbial fuel cells (MFC). *Int J Hydrogen Energy Aug.* 2013;38(26):11552–8.
- [25] Santoro C, Lei Y, Li B, Cristiani P. Power generation from wastewater using single chamber microbial fuel cells (MFCs) with platinum-free cathodes and pre-colonized anodes. *Biochem Eng J Mar.* 2012;62:8–16.
- [26] Abdi H, Williams LJ. Principal component analysis. *Wiley Interdiscip Rev Comput Stat Jul.* 2010;2(4):433–59.
- [27] Malaisrie SC, Malekzadeh S, Biedlingmaier JF. In vivo analysis of bacterial biofilm formation on facial plastic bioimplants. *Laryngoscope Nov.* 1998;108(11 Pt 1):1733–8.
- [28] Treter J, Macedo AJ. Catheters: a suitable surface for biofilm formation. *Sci Microb Pathog Commun Curr Res Technol Adv* 2011:835–42.
- [29] Fluoroplastic comparison – typical properties. [Online]. Available: [http://www2.dupont.com/Teflon\\_Industrial/en\\_US/tech\\_info/techinfo\\_compare.html](http://www2.dupont.com/Teflon_Industrial/en_US/tech_info/techinfo_compare.html) [accessed 01.03.14].
- [30] Polley MH, Boonstra BBST. Carbon blacks for highly conductive rubber. *Rubber Chem Technol Mar.* 1957;30(1):170–9.
- [31] Paganin VA, Ticianelli EA, Gonzalez ER. Development and electrochemical studies of gas diffusion electrodes for polymer electrolyte fuel cells. *J Appl Electrochem Mar.* 1996;26(3).
- [32] Giorgi L, Antolini E, Pozio A, Passalacqua E. Influence of the PTFE content in the diffusion layer of low-Pt loading electrodes for polymer electrolyte fuel cells. *Electrochim Acta Aug.* 1998;43(24):3675–80.